
INORGANIC CHEMISTRY

DOI 10.31489/2020Ch3/80-87

UDC 544.77: 541.64

L.M. Bogdanova¹, V.A. Lesnichaya¹, N.N. Volkova¹,
V.A. Shershnev¹, V.I. Irzhak¹, Yu.S. Bukichev², G.I. Dzhardimalieva^{1, 2*}

¹*Institute of Problems of Chemical Physics Russian Academy of Sciences, Chernogolovka, Moscow Region, Russia;*

²*Moscow Aviation Institute (National Research University), Moscow, Russia*

(Corresponding author's e-mail: dzhardim@icp.ac.ru)

Epoxy/TiO₂ composite materials and their mechanical properties

The physicomechanical properties and thermal stability of epoxy nanocomposites with TiO₂ (anatase — 75 %, rutile — 25 %) nanoparticles were studied. The TiO₂/epoxy polymer (TiO₂/EP) nanocomposite films were obtained by curing a pre-sonicated mixture of diane-epoxy resin ED-20, 4,4'-diaminodiphenylmethane and TiO₂ nanoparticles using stepwise technique: 90 °C for 3 hours, then 160 °C for 3 hours. Tensile tests were carried out according to American Society for Testing and Materials ASTM D882-10. The average size of TiO₂ nanoparticles and microstructure of the obtained nanocomposites were studied by scanning electron microscopy. It was found that addition of the TiO₂ nanoparticles at a concentration above 3 wt.% leads to a decrease in tensile strength at break, apparently due to secondary aggregation processes of nanoparticles. During curing, the average diameter of TiO₂ nanoparticles increases from 40 nm to 60 nm. An increase in the elastic modulus, a slight increase in the glass transition temperature, and a decrease in the elongation at break of epoxy nanocomposites at a concentration of TiO₂ nanoparticles > 1 wt.% indicate an increase in the rigidity of the epoxy matrix. The nanocomposites obtained were shown to be stable at concentrations of TiO₂ nanoparticles up to 5 wt.% and up to 300 °C in vacuum.

Keywords: epoxy resin, curing, titanium oxide (IV), nanoparticles, tensile strength at break, elastic modulus, elongation at break, thermal stability.

Introduction

The increasing requirements for modern materials lead to intensive search for new composite materials with additional properties (mechanical, magnetic, tribological, radiation protection, etc.). The introduction of inorganic nanoparticles into organic polymers is of considerable interest, because it makes possible to create the hybrid nanocomposite materials with improved properties such as heat resistance, fire resistance, reduced gas permeability, and resistance to chemicals. Titanium oxide (IV) (TiO₂) nanoparticles are often used as inorganic fillers of polymeric materials. Titanium oxide (IV) is one of the most widely used metal oxides for photocatalytic decomposition of organic pollutants in an aqueous or gaseous medium. The photoactivity of TiO₂ is based on the process of a reversible single-electron transition $Ti^{4+} + e^- \rightleftharpoons Ti^{3+}$. TiO₂ nanoparticles have a stronger photocatalytic effect than TiO₂ microparticles [1], forming reactive oxygen particles, hydroxyl radicals, H₂O₂, etc. under the influence of UV radiation. Due to exceptional characteristics of TiO₂, i.e. chemical and thermal stability, recycling potential, non-toxicity, and low cost, its applications range is quite wide: self-cleaning materials based on titanium oxide (IV), photocatalysts for the decomposition of organic compounds [2–6], anode materials [7,8], anti-bacterial coatings and packaging [9–12], etc. It is important to note that the induction of bactericidal activity due to photocatalysis is achieved by exposure to soft

* Corresponding author

ultraviolet (in the range of 360 nm), in contrast to the hard ultraviolet used in medicine, and is more effective than surface sterilization by ultraviolet [13].

Today one of the most pressing problems is the disposal of accumulated polymer waste, for example, based on thermoplastic materials widely used for the manufacture of packaging films, various containers and utensils for food and household purposes. Approaches based on the incineration of such waste have serious environmental consequences. One of the promising solutions to this problem is the use of polymeric materials, which contain titanium oxide nanoparticles and capable to active photodegradation under visible light. TiO₂-containing nanocomposites based on polystyrene [14], polyvinyl chloride [15], polyethylene [16, 17], polybenzyl methacrylate [18] showed significantly increased degradation rates under UV and sunlight irradiation, as compared to the pure polymers.

Containing TiO₂ nanoparticles thermoset nanocomposites have not been studied so extensively, but existing data show that TiO₂ nanoparticles are more effective than microparticles, for example in regard to mechanical properties. The effect of the size of filler particles on the mechanical properties of epoxy composite materials was studied in [19] using the example of TiO₂. Nano- (nanoparticles with a size of ~50 nm) and microcomposites (particles ~50 µm) were compared.

An increase in mechanical properties was observed at the content of nanoparticles up to 4 vol.%. The subsequent recession in properties is associated with enlargement of particles due to their agglomeration. In the case of microparticles the modulus grows while the strength decreases with filler concentration increasing. As it was shown by us earlier [20, 21], elastic and strength properties of epoxy nanocomposites are affected by both the size of nanoparticles as well as the structure of epoxy matrix and the crosslink density as shown by us earlier.

The purpose of this work was to obtain composites based on TiO₂ nanoparticles and an epoxy polymer (EP) prepared by polycondensation, and to study their mechanical properties.

Experimental

Materials

The schematic structure of the diane-epoxy resin ED-20 used in this work is shown in Figure 1a (epoxide group content is 22.6 %).

4,4'-Diaminodiphenylmethane (DDM) was purchased from Aldrich (Fig. 1, b). The scheme of polycondensation between epoxy ED-20 and DDM is shown in Figure 1, c.

Nanoparticles of TiO₂ have been prepared in the Institute of Problems of Chemical Physics of Russian Academy of Sciences using microwave irradiation [22], anatase 75 %, rutile 25 %, SSA = 33.0 m²/g, d_{av.} = 46 nm.

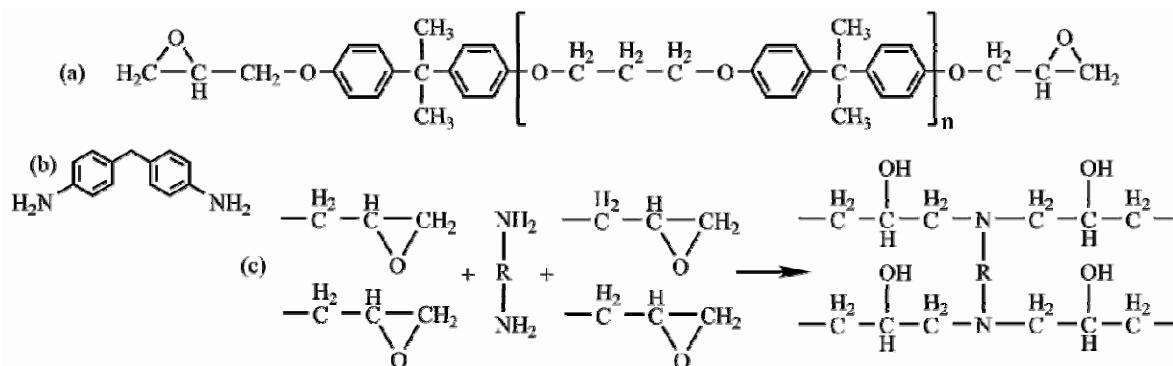


Figure 1. Structure of epoxy resin ED-20 (a); structure of DDM (b); scheme of polycondensation (c)

TiO₂/EP nanocomposite films of 80–100 µm thick were synthesized ex situ, i.e. using earlier prepared nanoparticles. The mixture of ED-20, DDM at equimolar ratio, and TiO₂ was heated slightly to dissolve DDM. Then it was degassed under low vacuum, and subjected to ultrasonic treatment using Sonorex Digital 10p instrument at 35 kHz for 40 min to disperse TiO₂ properly. The suspension obtained was poured between the two glass plates, which were put into a specially designed metal form and placed in an oven for further curing. The glass plates were pretreated with a solution of dimethyldichlorosilane in toluene to prevent adhesion. Mixtures were cured at stepwise increase of temperature, the conditions were determined based on calorimetric data in order to achieve a full cure (90 °C for 3 hours, 160 °C for 3 hours). The opaque, gray-blue

TiO₂/EP films were obtained as a result of curing. The film thickness was measured using a micrometer with a 10 microns accuracy.

The glass transition temperature of TiO₂/EP films was determined by differential scanning calorimetry (DSC) on a Mettler Toledo Star System instrument at a 5 deg/min temperature scan. Mechanical tensile tests were carried out according to ASTM D882-10 on a Zwick / Roell Z 010 universal machine at a 1 mm/min loading speed. Thermogravimetric analysis of the samples was carried out using ATW-14 electronic automatic vacuum thermobalance at a 2.4 deg/min constant heating rate in vacuum (residual pressure 1.2 Pa). Size of nanoparticles was determined using FESEM Zeiss Supra 25 on carbon-coated films.

Results and Discussion

Composition and microstructure of nanocomposites

TiO₂/EP nanocomposites were prepared by ex situ ultrasonic dispersion of TiO₂ nanoparticles in epoxy resin followed by curing in the presence of DDM. According to scanning electron microscopy (SEM) data, TiO₂ nanoparticles are fairly uniformly distributed in the volume of the polymer matrix, nevertheless, nanoparticles aggregation is still observed (Fig. 2). Particle size distribution shows that during curing the average size of nanoparticles increases (from 46 nm to 78 nm at 0.5 wt.% TiO₂).

Physicomechanical properties

As can be seen from the data in Figure 3, T_g weakly depends on the TiO₂ concentration, however, it tends to slightly decrease (173 °C — 167 °C) at <1 wt.% concentrations and increase (167 °C — 173 °C) at up to 5 wt.% concentrations. The concentration dependence of the elasticity modulus shows similar behavior with 27 % increase in modulus at 3 wt.% concentration

Tensile strength at break decreases sharply at TiO₂ more than 3 wt.% concentrations, which is probably due to secondary agglomeration of TiO₂ (Fig. 4). Therefore, the working concentration should not exceed 3 wt.% TiO₂. The average diameter of TiO₂ increases (from 40 to 60 nm at 0.5 wt.% TiO₂ concentration) during curing. The change in strain at break varies by TiO₂ concentration: less than 1 wt.% concentrations cause its increase, while more than 1 wt.% concentrations cause its decrease. A significant decrease in strain at break by almost 80 % indicates a loss of plasticity and an increase in brittleness. This is consistent with an increase in elastic modulus and glass transition temperature at above 1 wt.% TiO₂ concentrations.

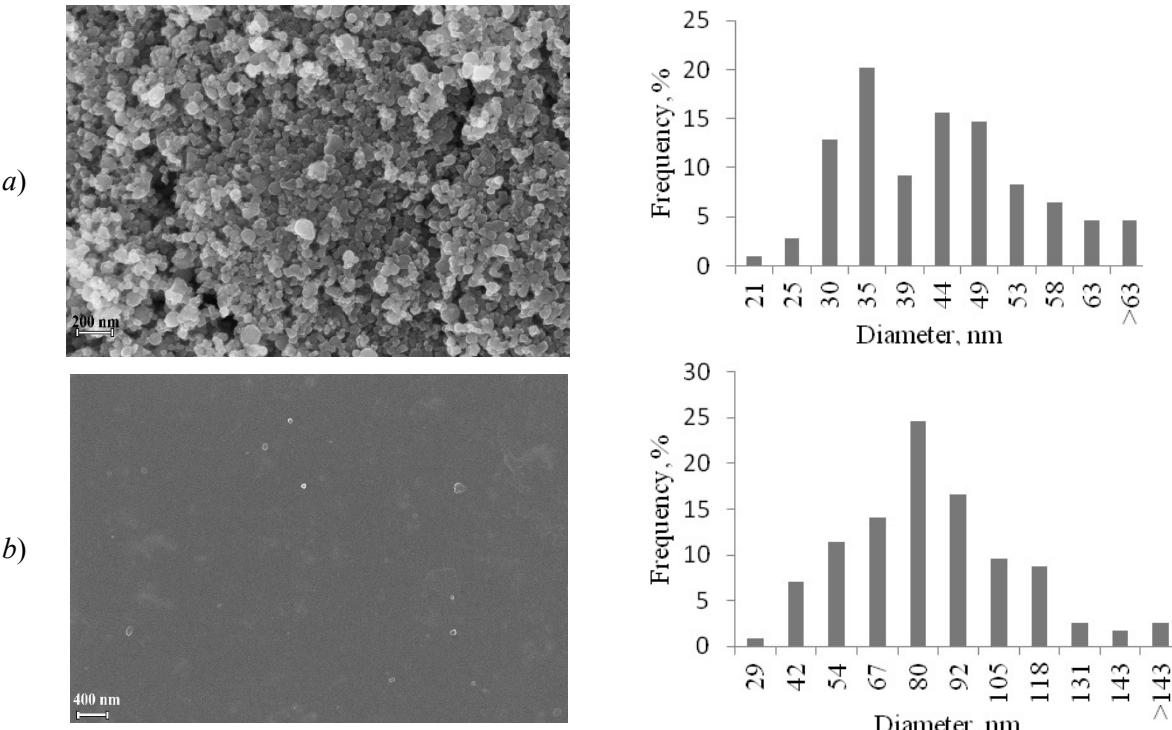
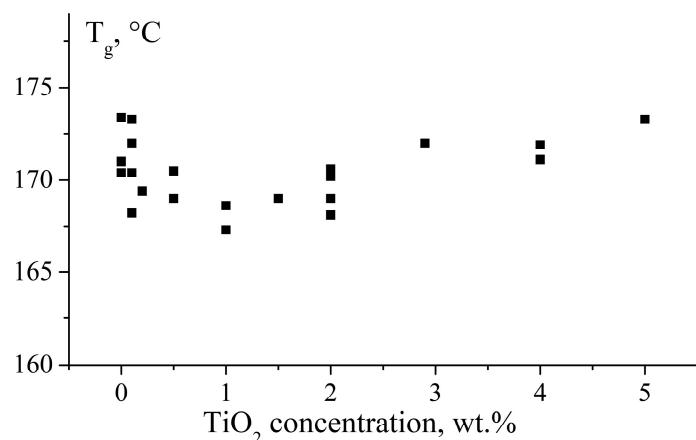
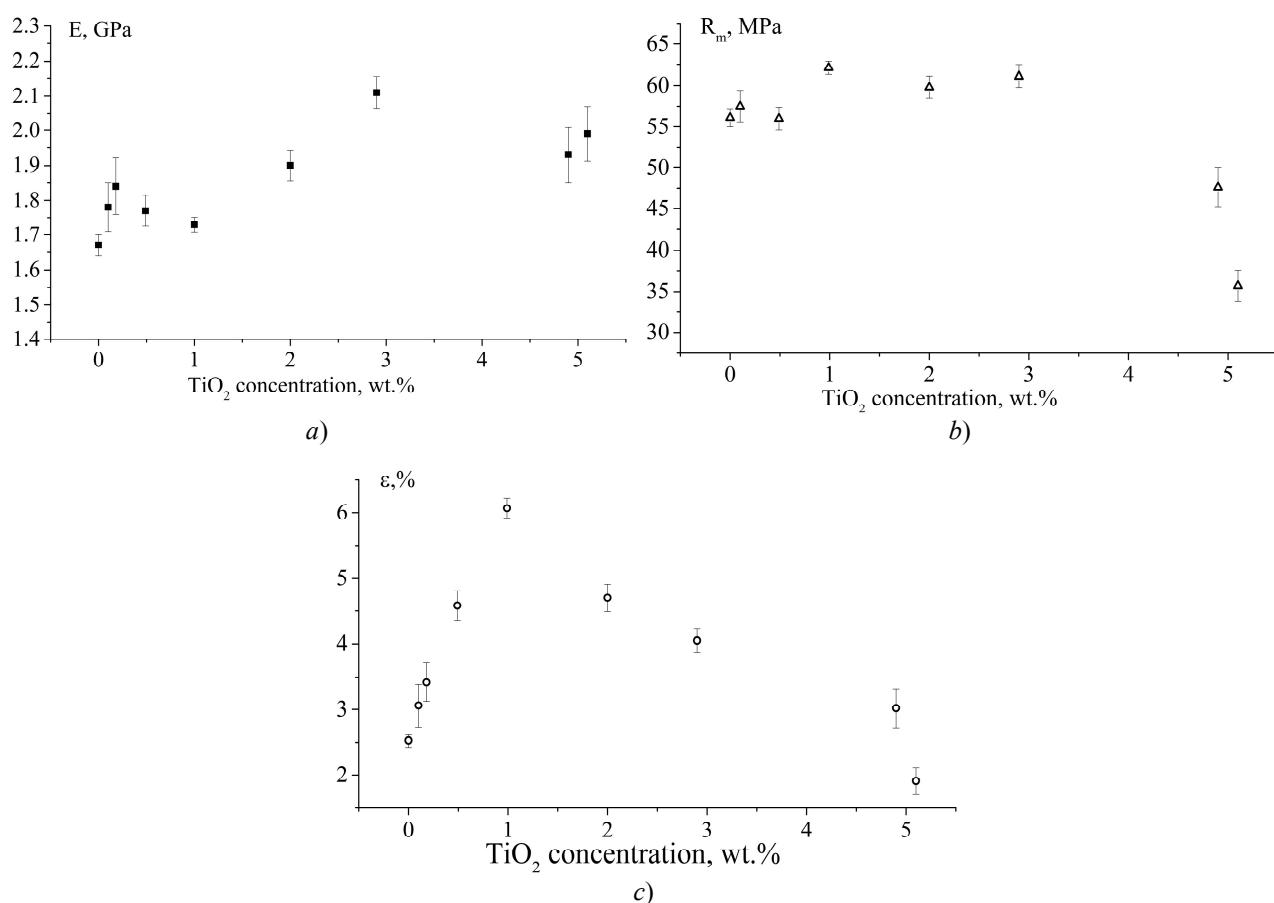


Figure 2. Scanning electron microscope (SEM) image and particle size distribution for TiO₂ nanoparticles (a) and TiO₂/EP nanocomposite with 0.5 wt.% of TiO₂ (b)

Figure 3. Tg dependence of TiO₂/EP nanocomposites on the concentration of TiO₂ nanoparticles

a — elastic modulus, GPa; b — tensile strength at break, MPa; c — strain at break, %

Figure 4. The dependence of the mechanical properties of TiO₂/EP nanocomposites on the concentration of TiO₂

Thermal stability of nanocomposites

Stability of nanocomposites is essential for its implementation. Therefore, the thermal stability of TiO₂/EP films with different concentrations of TiO₂ was studied. As can be seen from Figure 5, TiO₂/EP are stable at up to 5 wt.% TiO₂ concentrations and up to 300 °C temperatures in vacuum.

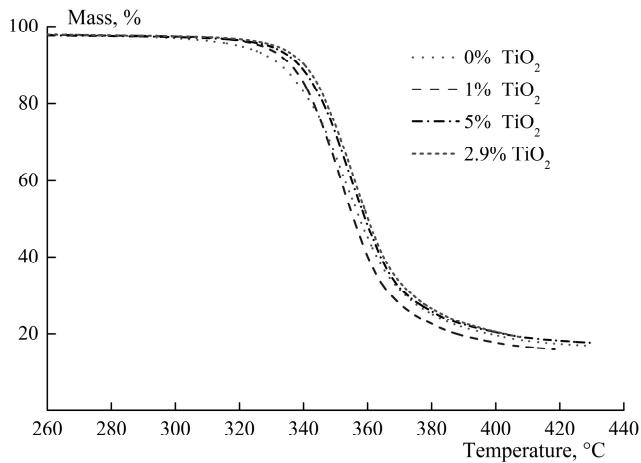


Figure 5. Thermograms of TiO_2/EP nanocomposites with 1–5 wt.% filler concentration
(2.4 °C/min heating rate; 1.3 Pa residual pressure)

The results obtained are in good agreement with the literature. It was found that $\text{TiO}_2/\text{polypropylene}$ nanocomposites have the similar thermal stability in the nitrogen atmosphere [23]. The initial and maximum decomposition temperatures increase from 360 °C and 455 °C for the EP to 405 °C and 479 °C for the polymer nanocomposites with 2 wt % TiO_2 content.

Conclusions

The TiO_2/EP nanocomposites with 0.5–5 wt.% filler content were obtained by ex situ introduction of TiO_2 nanoparticles into the epoxy resin ED-20 at the stage of curing in the presence of 4,4'-diaminodiphenylmethane. It was found that the addition of TiO_2 nanoparticles at a concentration above 3 wt. % leads to a decrease in tensile strength at break, apparently due to secondary aggregation processes. The average diameter of TiO_2 nanoparticles increases from 46 nm to 80 nm during curing. An increase in the elastic modulus, a slight increase in the glass transition temperature and a drop in the elongation at break of the epoxy nanocomposite at concentrations of TiO_2 nanoparticles above 1 wt. %, indicate an increase in the rigidity of the nanocomposite matrix. The stability of TiO_2/EP in vacuum is shown at temperatures up to 300 °C and filler concentrations up to 5 wt.%.

This work was performed in accordance with the state task, state registration No. AAAA-A19-119032690060-9 using the equipment of the Multi-User Analytical Center of IPCP RAS.

References

- 1 Fujishima A. Titanium Dioxide Photocatalysis / A. Fujishima, T.N. Rao, D.A. Tryk // Journal of Photochemistry and Photobiology C: Photochemistry Reviews. — 2000. — No. 1. — P. 1–21.
- 2 Hamdy M.S. A Novel TiO_2 Composite for Photocatalytic Wastewater Treatment / M.S. Hamdy, W.H. Saputera, E.J. Groenen, G. Mul // Journal of Catalysis. — 2014. — Vol. 310. — P. 75–83. DOI: 10.1016/j.jcat.2013.07.017.
- 3 Song L. Photodegradation of phenol in polymer-modified TiO_2 semiconductor particulate system under the irradiation of visible light / L. Song, R. Qiu, Y. Mo, D. Zhang, H. Wei, Y. Xiong // Catalysis Communication. — 2007. — Vol. 8. — P. 429–433.
- 4 Truppi A. Visible-light-active TiO_2 -based hybrid nanocatalysts for environmental applications / A. Truppi, F. Petronella, T. Placido, M. Striccoli, A. Agostiano, M.L. Curri, R. Comparelli // Catalysts. — 2017. — Vol. 7, Iss. 4. — P. 100. <http://dx.doi.org/10.3390/catal7040100>.
- 5 Khalid N.R. Carbonaceous- TiO_2 nanomaterials for photocatalytic degradation of pollutants: A review / N.R. Khalid, A. Majid, M. Bilal Tahir, N.A. Niaz, Sadia Khalid // Ceramics International. — 2017. — Vol. 43. — P. 14552–14571. <http://dx.doi.org/10.1016/j.ceramint.2017.08.143>.
- 6 Zhou, T.-T. Flexible $\text{TiO}_2/\text{PVDF}/\text{g-C3N4}$ Nanocomposite with Excellent Light Photocatalytic Performance / T.-T. Zhou, F.-H. Zhao, Y.-Q. Cui, L.-X. Chen, J.-S. Yan, X.-X. Wang, Y.-Z. Long // Polymers. — 2020. — Vol. 12, No. 55. doi:10.3390/polym12010055.
- 7 Bella F. Combined Structural, Chemometric, and Electrochemical Investigation of Vertically Aligned TiO_2 Nanotubes for Na-ion Batteries / F. Bella, A.B. Muñoz-García, F. Colò, G. Meligrana, A. Lamberti, M. Destro, M. Pavone, C. Gerbaldi // ACS Omega. — 2018. — Vol. 3. — P. 8440–8450. DOI: 10.1021/acsomega.8b01117.
- 8 Liu S. TiO_2 nanorods grown on carbon fiber cloth as binder-free electrode for sodium-ion batteries and flexible sodium-ion capacitors / S. Liu, Z. Luo, G. Tian, M. Zhu, Z. Cai, A. Pan, S. Liang // Journal of Power Sources. — 2017. — Vol. 363. — P. 284–290.

9 Murugan K. Synthesis, Characterization and Demonstration of Self-Cleaning TiO₂ Coatings on Glass and Glazed Ceramic Tiles / K. Murugan, R. Subasri, T.N. Rao et al. // Progress in Organic Coatings. — 2013. — Vol. 76, No. 12. — P. 1756–1760. DOI 10.1016/j.porgcoat.2013.05.012.

10 Nandagopal S. Gentamicin Loaded Electrospun Poly(ε-Caprolactone)/TiO₂ Nanocomposite Membranes with Antibacterial Property against Methicillin Resistant Staphylococcus aureus / S. Nandagopal, A. Robin, C.G. Soney, V.P. Jayachandran, K. Nandakumar, T. Sabu // Journal of Polymer-Plastics Technology and Engineering. — 2016. — Vol. 55. — P. 1785–1796. <https://doi.org/10.1080/03602559.2016.1171877>.

11 Li Q. Enhanced visible light-induced photocatalytic disinfection of E. coli by carbon sensitized nitrogen-doped titanium oxide / Q. Li, R. Xie, Y.W. Li, E.A. Mintz, J.K. Shang // Environmental Science Technology. — 2007. — Vol. 41. — P. 5050–5056.

12 Bodaghi H. Synthesis of clay-TiO₂ nanocomposite thin films with barrier and photocatalytic properties for food packaging application / H. Bodaghi, Y. Mostofi, A. Oromiehie, B. Ghanbarzadeh, Z.G. Hagh // Journal of Applied Polymer Science. — 2015. — Vol. 132. — Article number 41764. DOI: 10.1002/app.41764.

13 Проданчук Н.Г. Наночастицы диоксида титана и их потенциальный риск для здоровья и окружающей среды / Н.Г. Проданчук, Г.М. Балан // Сучасні проблеми токсикології (Современные проблемы токсикологии). — 2011. — № 4. — С. 11–27.

14 Zang L. Solid-phase photocatalytic degradation of polystyrene with modified Nano-TiO₂ catalyst / L. Zang, S. Wang, W. Fa, Y. Hu, L. Tian, K. Deng // Polymer. — 2006. — Vol. 47, No. 24. — P. 8155–8162. doi:10.1016/j.polymer.2006.09.023.

15 Kim S.H. Photocatalytic degradation of flexible PVC / TiO₂ nano hybrid as an eco-friendly alternative to the current waste landfill and dioxin-emitting incineration of post-use PVC / S.H. Kim // Polymer. — 2006. — Vol. 47. — P. 3005–3016.

16 Li Sh. Photocatalytic degradation of polyethylene plastic with polypyrrole/TiO₂ nanocomposite as photocatalyst / Sh. Xu, L. He, F. Xu, Y. Wang, L. Zhang // Polymer-plastics technology and engineering. — 2010. — Vol. 49, No. 4. — P. 400–406.

17 Zhao X. Solid-phase photocatalytic degradation of polyethylene plastic under UV and solar light irradiation / X. Zhao, Z. Li, Y. Chen, Y. Zhu // Journal of molecular catalysis A: Chemical. — 2007. — Vol. 268. — P. 101–106.

18 Данг К.Н. Нанодиоксид титана в полимерных матрицах и фотопревращения с его участием / К.Н. Данг, Н.В. Сидоренко, Е.В. Евстратова, М.А. Ваниев, И.А. Новаков // Изв. вузов. «Технология легкой промышленности». — 2011. — Т. 12, № 2. — С. 97–103.

19 Al-Ajaj I.A. Mechanical Properties of Micro and Nano TiO₂/Epoxy Composites / I.A. Al-Ajaj, M.M. Abd, H.I. Jaffer // International Journal of Mining, Metallurgy & Mechanical Engineering. — 2013. — Vol. 1, No. 2. — P. 93–97.

20 Богданова Л.М. Механические свойства эпоксидных композитов на основе наночастиц серебра, сформированных *in situ* / Л.М. Богданова, Л.И. Кузуб, Э.А. Джавадян, В.И. Торбов, Н.Н. Дрёмова, А.Д. Помогайло // Высокомолекулярные соединения. Сер. А. — 2014. — Т. 56, № 3. — С. 289–295.

21 Богданова Л.М. Эволюция наночастиц серебра, синтезированных *in situ*, в стеклообразной эпоксидной матрице / Л.М. Богданова, В.А. Шершнев, М.Г. Спирин, В.И. Иржак, С.Е. Закиев, Г.И. Джардимилиева // Журн. физ. хим. — 2019. — Т. 93, № 7. — С. 1043–1047.

22 Берестенко В.И. Микроволновой хлоридный процесс получения диоксида титана / В.И. Берестенко, В.И. Торбов, В.И. Чукалин, Е.Н. Куркин, И.Л. Балихин, И.А. Домашнев, В.Н. Троицкий, С.В. Гуров // Химия высоких энергий. — 2011. — Т. 45, № 5. — С. 468–472.

23 Esthappan S.K. Effect of titanium dioxide on the thermal ageing of polypropylene / S.K. Esthappan, S.K. Kuttappan, R. Joseph // Polymer Degradation Stability. — 2012. — Vol. 97. — P. 615–620.

Л.М. Богданова, В.А. Лесничая, Н.Н. Волкова,
В.А. Шершнев, В.И. Иржак, Ю.С. Букичев, Г.И. Джардимилиева

TiO₂ эпоксидті нанокомпозиттері және олардың механикалық қасиеттері

TiO₂ (анатаз — 75 %, рутил — 25 %) нанобөлшектері бар поликонденсациялық эпоксидті нанокомпозиттердің физика-механикалық қасиеттері және термотұрактылығы зерттелген. Эпоксидті полимер (TiO₂/ЭП) негізіндегі калындығы 80–100 мкм нанокомпозитті қабықшалар алдын-ала ультратұраудыбыспен өндөлген эпоксидианды шайыр, 4,4'-диаминдифенилметан және TiO₂ нанобөлшектерінің коспасын сатылы температуралық режим бойынша (90 °C — 3 сағ) + (160 °C — 3 сағ) катаиту арқылы алынды. Созылуға механикалық сынактар ASTM D882–10 стандарты бойынша жүргізілді. TiO₂ нанобөлшектерінің өлшемдері мен альянған нанокомпозиттердің микротұраудыларды сканерлеуші электрондық микроскопия әдісімен зерттелді. TiO₂ нанобөлшектерін 3 масс. % жоғары косу нанобөлшектер агрегациясының екіншілік процестері салдарынан беріктіктің төмендеуіне әкеледі. Қатаю процесінде TiO₂ нанобөлшектерінің орташа диаметрі 40 нм-ден 60 нм-ге дейін артады. TiO₂ нанобөлшектерінің концентрациясы >1 масс. % кезінде серпімділік модулінің ұлғаюы, шынылану температурасының жоғарылау тенденциясы және эпоксидті нанокомпозиттердің деформациясының төмендеуі эпоксидті матрицаның қаттылығының артқанын көрсетеді. TiO₂ нанобөлшектерінің концентрациясы 5 масс. % дейін болғанда және вакумда 300 °C-ка дейінгі температураларда зерттелген нанокомпозиттердің тұрақтылығы көрсетілген.

Кілт сөздер: эпоксидті шайыр, катаю, титан диоксиді, нанобөлшектер, механикалық қасиеттер, термиялық тұрақтылық.

Л.М. Богданова, В.А. Лесничая, Н.Н. Волкова,
В.А. Шершнев, В.И. Иржак, Ю.С. Букичев, Г.И. Джардималиева

TiO₂ эпоксидные нанокомпозиты и их механические свойства

Исследованы физико-механические свойства и термостабильность поликонденсационных эпоксидных нанокомпозитов с наночастицами TiO₂ (анатаз — 75 %, рутил — 25 %). Нанокомпозитные плёнки на основе эпоксидного полимера (TiO₂/ЭП) толщиной 80–100 мкм получали отверждением предварительно обработанной ультразвуком смеси эпоксидаиновой смолы ЭД-20, 4,4'-диаминодифенилметана и наночастиц TiO₂ по ступенчатому температурному режиму (90 °C — 3 ч) + (160 °C — 3 ч). Механические испытания на растяжение проводили по стандарту ASTM D882-10. Размеры наночастиц TiO₂ и микроструктуру полученных нанокомпозитов изучали методом сканирующей электронной микроскопии. Найдено, что добавление наночастиц TiO₂ выше концентрации 3 масс.% приводит к падению прочности, по-видимому, вследствие вторичных процессов агрегации наночастиц. В процессе отверждения средний диаметр наночастиц TiO₂ возрастает от 40 до 60 нм. Увеличение модуля упругости, тенденция к повышению температуры стекловидания и падение деформации эпоксидных нанокомпозитов при концентрациях наночастиц TiO₂ > 1 масс.% свидетельствуют о повышении жёсткости эпоксидной матрицы. Показана стабильность изученных нанокомпозитов при концентрациях наночастиц TiO₂ до 5 масс.% и температурах до 300 °C в вакууме.

Ключевые слова: эпоксидная смола, отверждение, диоксид титана, наночастицы, механические свойства, термическая стабильность.

References

- 1 Fujishima, A.T., Rao, N., & Tryk, D.A. (2000). Titanium Dioxide Photocatalysis. *Journal of Photochemistry and Photobiology C: Photochemistry Reviews*, 1, 1–21.
- 2 Hamdy, M.S., Saputera, W.H., Groenen, E.J., & Mul G. (2014). A Novel TiO₂ Composite for Photocatalytic Wastewater Treatment. *Journal of Catalysis*, 310, 75–83. DOI: 10.1016/j.jcat.2013.07.017
- 3 Song, L., Qiu, R., Mo, Y., Zhang, D., Wei, H., & Xiong Y. (2007). Photodegradation of phenol in polymer-modified TiO₂ semiconductor particulate system under the irradiation of visible light. *Catalysis Communication*, 8, 429–433.
- 4 Truppi, A., Petronella, F., Placido, T., Striccoli, M., Agostiano, A., Curri, M.L., & Comparelli, R. (2017). Visible-light-active TiO₂-based hybrid nanocatalysts for environmental applications. *Catalysts*, 7(4), 100. <http://dx.doi.org/10.3390/catal7040100>.
- 5 Khalid, N.R., Majid, A., Tahir, M.B., Niaz, N.A., & Khalid, S. (2017). Carbonaceous-TiO₂ nanomaterials for photocatalytic degradation of pollutants: A review. *Ceramics International*, 43, 14552–14571. <http://dx.doi.org/10.1016/j.ceramint.2017.08.143>.
- 6 Zhou, T.-T., Zhao, F.-H., Cui, Y.-Q., Chen, L.-X., Yan, J.-S., Wang, X.-X., & Long, Y.-Z. (2020). Flexible TiO₂/PVDF/g-C3N4 Nanocomposite with Excellent Light Photocatalytic Performance. *Polymers*, 12(55). doi:10.3390/polym12010055.
- 7 Bella, F., Muñoz-García, A.B., Colò, F., Meligrana, G., Lamberti, A., Destro, M., Pavone, M., & Gerbaldi C. (2018). Combined Structural, Chemometric, and Electrochemical Investigation of Vertically Aligned TiO₂ Nanotubes for Na-ion Batteries. *ACS Omega*, 3, 8440–8450. DOI: 10.1021/acsomega.8b01117.
- 8 Liu, S., Luo, Z., Tian, G., Zhu, M., Cai, Z., Pan, A., & Liang, S. (2017). TiO₂ nanorods grown on carbon fiber cloth as binder-free electrode for sodium-ion batteries and flexible sodium-ion capacitors. *Journal of Power Sources*, 363, 284–290.
- 9 Murugan, K., Subasri, R., Rao, T.N., Gandhi, A.S., & Murty, B.S. (2013). Synthesis, characterization and demonstration of self-cleaning TiO_x coatings on glass and glazed ceramic tiles. *Progress in Organic Coatings*, 76(12), 1756–1760. doi:10.1016/j.porgcoat.2013.05.012.
- 10 Nandagopal, S., Robin, A., Soney, C.G., Jayachandran, V.P., Nandakumar, K., & Sabu, T. (2016). Gentamicin Loaded Electrospun Poly(ϵ -Caprolactone)/TiO₂ Nanocomposite Membranes with Antibacterial Property against Methicillin Resistant Staphylococcus aureus. *Journal of Polymer-Plastics Technology and Engineering*, 55, 1785–1796. <https://doi.org/10.1080/03602559.2016.1171877>.
- 11 Li, Q., Xie, R., Li, Y.W., Mintz, E.A., & Shang, J.K. (2007). Enhanced visible light-induced photocatalytic disinfection of E. coli by carbon sensitized nitrogen-doped titanium oxide. *Environmental Science Technology*, 41, 5050–5056.
- 12 Bodaghi, H., Mostofi, Y., Oromiehie, A., Ghanbarzadeh, B., & Hagh, Z.G. (2015). Synthesis of clay-TiO₂ nanocomposite thin films with barrier and photocatalytic properties for food packaging application. *Journal of Applied Polymer Science*, 132, 41764. DOI: 10.1002/app.41764.
- 13 Prodanchuk, N.G., & Balan, G.M. (2011). Nanochastitsy dioksida titana i ikh potentsialnyi risk dlja zdorovija i okruzhayushchej sredy [Titanium dioxide nanoparticles and their potential health and environmental risks]. *Sovremennye problemy toksikologii — Modern problems of toxicology*, 4, 11–27 [in Russian].
- 14 Zang, L., Wang, S., Fa, W., Hu, Y., Tian, L., & Deng, K. (2006). Solid-phase photocatalytic degradation of polystyrene with modified Nano-TiO₂ catalyst. *Polymer*, 47(24), 8155–8162. doi:10.1016/j.polymer.2006.09.023.
- 15 Kim, S.H. (2006). Photocatalytic degradation of flexible PVC / TiO₂ nano hybrid as an eco-friendly alternative to the current waste landfill and dioxin-emitting incineration of post-use PVC. *Polymer*, 47, 3005–3016.
- 16 Xu, Sh., He, L., Xu, F., Wang, Y., & Zhang L. (2010). Photocatalytic degradation of polyethylene plastic with polypyrrole/TiO₂ nanocomposite as photocatalyst. *Polymer-plastics technology and engineering*, 49(4), 400–406.

- 17 Zhao, X., Li, Z., Chen, Y., & Zhu, Y. (2007). Solid-phase photocatalytic degradation of polyethylene plastic under UV and solar light irradiation. *Journal of molecular catalysis A: Chemical*, 268, 101–106.
- 18 Dang, K.N., Sidorenko, N.V., Evstratova, E.V., Vaniev, M.A., & Novakov, I.A. (2011). Nanodioksid titana v polymernykh matritsakh i fotoprevrashcheniya s eho uchastiem [Titanium nanodioxide in polymer matrices and phototransformations with its participation]. *Izvestiia vuzov. «Technologiya lehkoi promyshlennosti» — University Bulletin. Light industry technology*, 12(2), 97–103 [in Russian].
- 19 Al-Ajaj, I.A., Abd, M.M., & Jaffer, H.I. (2013). Mechanical Properties of Micro and Nano TiO₂/Epoxy Composites. *International Journal of Mining, Metallurgy & Mechanical Engineering*, 1(2), 93–97.
- 20 Bogdanova, L.M., Kuzub, L.M., Dzhavadyan, E.A., Torbov, V.I., Dryemova, N.N., & Pomogailo, A.D. (2014). Mekhanicheskie svoistva epoksidnykh kompozitov na osnove nanochastits serebra, sformirovannykh *in situ* [Mechanical properties of epoxy composites based on Ag nanoparticles produced *in situ*]. *Vysokomolekuliarnye soedineniya. Seriya A — Polymer science. A*, 56(3), 289–295 [in Russian].
- 21 Bogdanova, L.M., Shershnev, V.A., Spirin, M.G., Irzhak, V.I., Zakiev, S.E., & Dzhardimalieva, G.I. (2019). Evolutsiya nanochastits serebra, sintezirovannykh *in situ*, v stekloobraznoi epoksidnoi matritse [Evolution of Ag nanoparticles produced *in situ* in epoxy matrix]. *Zhurnal fizicheskoi khimii — Journal of physical chemistry*, 93(7), 1043–1047 [in Russian].
- 22 Berestenko, V.I., Torbov, V.I., Chukalin, V.I., Kurkin, E.N., Balikhin, I.L., Domashnev, I.A., Troitskii, V.N., & Gurov, S.V. (2011). Mikrovolnovoi khloridnyi protsess polucheniia dioksida titana [Microwave chloride process for producing titanium dioxide]. *Khimia vysokikh enerhii — High energy chemistry*, 45(5), 468–472 [in Russian].
- 23 Esthappan, S.K., Kuttappan, S.K., & Joseph, R. (2012). Effect of titanium dioxide on the thermal ageing of polypropylene. *Polymer Degradation Stability*, 97, 615–620.